

INTRODUCTION TO FOAMABILITY STUDY OF A LDPE SUBJECTED TO GAMMA RADIATION

Elizabeth C. L. Cardoso¹, Sandra R. Scagliusi¹, Duclerc F. Parra¹ and Ademar B. Lugão¹

*1 – Centro de Química e Meio Ambiente - Instituto de Pesquisas Energéticas e Nucleares-
(IPEN / CNEN – SP, Brazil)*

corresponding author: eclcardo@ipen.br

Abstract – Nowadays, polymer foams have a wide application area due to their light weight, emphasizing resistance to impact, high thermal insulation and damping properties, among others. So, automotive, packing industry, electronic, aerospace, building construction, bedding and even medical applications are some of the fields where polymer foams are been applied. Foams can be classified as open and closed: Closed-cell foam is provided with tiny and discrete pockets of gas, each one totally enclosed within polymer walls; open cell foam has tiny cells which are not completely closed. In this work, LDPE (Low Density Polyethylene) resin foamability was investigated after exposure to ionizing radiation (gamma), at 5, 10 and 15 kGy. Characterizations included: Melt Flow Index, Melt Strength and Scanning Electron Microscopy.

Keywords: *LDPE, foams, melt strength, gamma-radiation.*

Introduction

Ionizing radiation is commonly used for modifying polymers and optimization of their properties is widely used in literature [1-3]. Ionizing radiation, via e-beam or gamma rays is comprehensively used in LDPE chain branching: irradiation increases molar mass and, consequently, melt resistance [4]. Chain branching occurs when the polymer is radiated with a minimal dose, resulting in formation of side chains, improving its melt processability. Long chain branching (LCB) makes the resin more sensible to shear: so, for an adequate processing, it should be avoided the operation with materials with very low melt index, to avoid an undesirable high pressure in the extruder [5-6]. It is known that LDPE melt strength raises in function of melt index [7-8], but it is required a balance between these two parameters, on behalf of a safe and effective polymer processing. Rheology poses a fundamental relevance in polymer processing and establishes more favorable conditions in transformation processes. The behavior of thermoplastics flow, during the processing, depends of molar mass, distribution and branching [9-10]. When LDPE is subjected to high temperatures, there is a decrease in thermal resistance and mechanical properties, especially in foaming. The use of low irradiation doses (up to 30 kGy) will improve the processability, on behalf of a more resistant and thermally more stable matrix [11]. Melt strength of LDPE irradiated [12] is optimized in function of irradiation: besides, a raise in LCB observed in irradiated polymers enhances strain hardening [13-14] and it is responsible by an effective polymer foaming with build-up of cells exhibiting more resistant walls. LDPE foaming via Physical Blowing Agent (PBA) presents a weak balance between melt strength of melt polymer in expansion and cells internal pressure, occurring in a melting temperature close to polymer crystallization temperature. Foams are created via dissolution of a gas

in LDPE melt, expanding into small bubbles or cells, ending with the cooling of expanded polymeric mass [15-16].

This work aims to investigate resin foamability of a LDPE exposed to ionizing radiation (gamma), at low levels: 5, 10 and 15 kGy.

Experimental

Samples

LDPE, EB 853, from Quattor.

LDPE gamma radiated, ^{60}Co source, 5, 10 and 15 kGy, at 5kGy/h, Multipurpose reactor, in CETER/IPEN.

Melt Flow Index

Melt Flow Index analyses were accomplished in a Ceast apparatus, modular line, at 190 °C, 2.16 kg load, 240 seconds pre-heating, in accordance with ASTM D1238-04C.

Melt Strength

Haake extruder was connected to Rheotens 71.97 Göttfert, according shown in Figures 1 and 2:

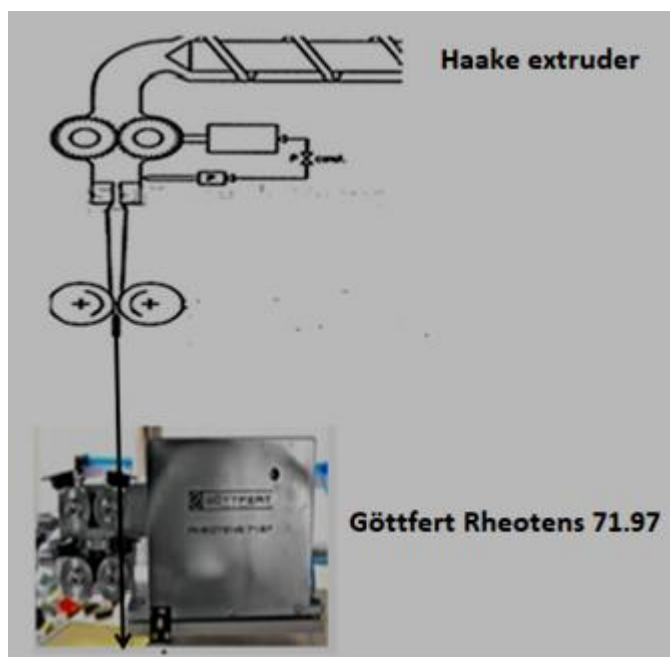


Figure 1. Scheme of Haake extruder connected to Rheotens 71.97 apparatus.



Figure 2. Haake extruder.

Foaming

Samples irradiated and non-irradiated were subjected to foaming process, by Physical Blowing Agent (Carbon Dioxide – CO₂), in Haake extruder, specific mono-screw, at 30 bar pressure, by using a pressure valve connected to Haake extruder, according to Figure 3:

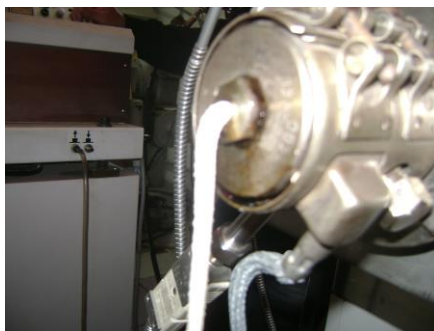


Figure 3. Foaming operation, by using a rectangular die.

Scanning Electron Microscopy

Foamed samples were further analyzed in a FEG equipment model F-50 in powder previously gold coated in a Balzers SCD 050 sputtering system.

Results and discussion

Malt Index and Melt Strength;

In Table 1 are shown results for LDPE analyzed:

Table 1. Melt Index and Melt Strength for LDPE, irradiated and non-irradiated.

	Melt Index (g.10min ⁻¹)	Melt Strength, 200°C (cN)
0 kGy	2.62	1.5
5 kGy	1.45	2.3
10 kGy	1.01	3.1
15 kGy	None flow	5.8

Scanning Electron Microscopy

Samples from Table 1 presented following micrographies when investigated in FEG equipment:

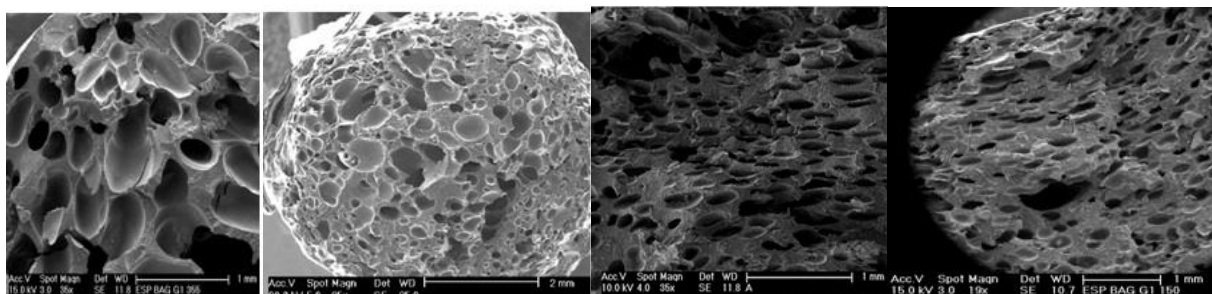


Figure 4. Micrographies for 0, 5, 10 and 15 kGy, respectively, from left to right.

Conclusions

Ionizing radiation, via gamma, within 5 to 15 kGy, contributed for a raise in closed cells, according it is shown in obtained micrographies, emphasizing that even non-irradiated LDPE presented discrete closed cells. Nevertheless, there should be a balance between processability, indicated by melt index, and closed cells generation, in order to avoid an undesirable high pressure in extruder. It

was not possible to obtain a Melt Index reading for LDPE irradiated at 15 kGy sample, that presented a dramatically high result for Melt Strength.

Acknowledgements

The authors thank Quattor by LDPE supply and Ipen/CNEN – SP by irradiation and financial support.

References

1. Charlesby A., Atomic Radiation and Polymers, *Pergamon Press*, New York, 1990.
2. Woods, R.; Pikaev, A., Applied Radiation Chemistry, *Radiation Processing*, Wiley, New York, 1994.
3. Yongxia Sun and Andrzej G. Chmielewski, *Applications of ionizing radiation in materials processing*, 2017.
4. L.A. Utracki, *Polymer Blends*, Rapra Review Report, **11**, Report 123, 2000.
5. K. Makuuchi and Song Cheng in *Radiation Processing of Polymer materials and its Industrial Applications*, Wiley, New York, 2012.
6. M. Bradley and E. Phillips, *SPE ANTEC Technical Papers*, **36**, 717, 1990.
7. A. Ghijssels, J. Ente and J. Raadsen, *International Polymer Processing*, **5**, 284-286, 1990.
8. D. Kerluke, S. Cheng and G. Forczek, *SPE Polyolefins Conference*, Houston, 2004.
9. B. Kazatchkov, *Polymer Engineering and Science*, **39**, 4, 1999.
10. Makuuchi K., S. Cheng, *Radiation Processing of Polymer Materials and Its Industrial Applications*, Nova York: John Wiley & Sons Inc, p.1, 2012.
11. Zhao W., Pan X., *Technology of Radiation Processing and its Applications*, Beijing, China: Weapon Industry, 2003.
12. M. H. Wagner, A. Bernnat, The rheology of Rheotens test, *J. Rheol.* **42** (4), 1998.
13. Song Cheng, Edward Phillips, Lewis Parks, Improving Processability of Polyethylenes by Radiation-Induced Long Chain Branching, *Radiation Physics and Chemistry* **78**, 563-566, 2009.
14. James L. Throne, *Thermoplastic Foam Extrusion*, Hanser, 3.15, pp32, 2004.
15. S.M.Tamboly, S.T.Mhaske, D.D.Kale, Crosslinked Polyethylene, *Indian Journal of Chemical Technology*, **11**, pp 853-864, 2004.
16. H. P. A de Deus and M. K. Alves, An application for polymeric foams, *Mechanics of Solids in Brazil*, 2009.